

# Lecture 3, Structure. 3.054

## Structure of cellular solids

### 2D honeycombs:

- Polygonal cells pack to fill 2D plane
- Prismatic in 3<sup>rd</sup> direction

Fig.2.3a



### 3D foams:

- Polyhedral cells pack to fill space

Fig.2.5

### Properties of cellular solid depend on:

- Properties of solid it is made from ( $\rho_s, E_s, \sigma_{ys} \dots$ )
- Relative density,  $\rho^*/\rho_s$  (= volume fraction solids)
- Cell geometry
- Cell shape    anisotropy
- Foams - open vs. closed cells
  - open:** Solid in edges only; voids continuous
  - closed:** Faces also solid; cells closed off from one another
- Cell size - typically not important

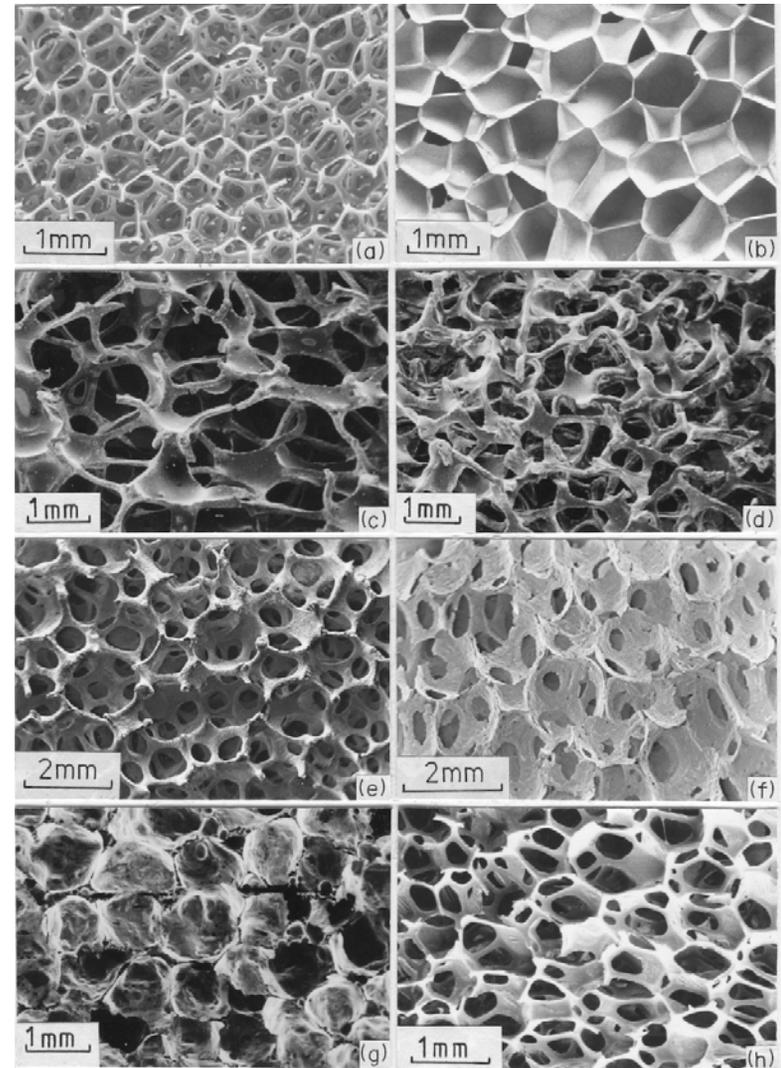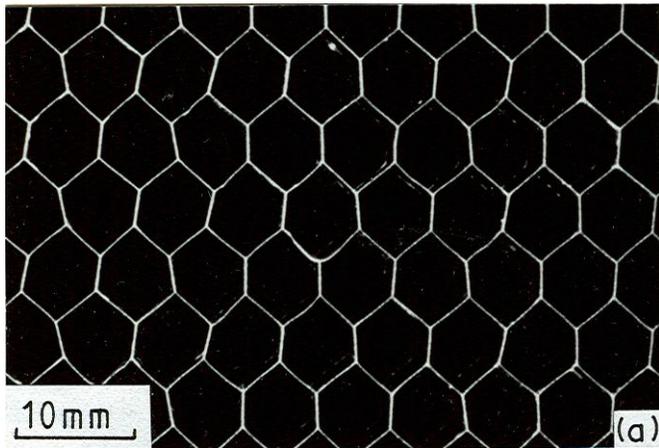

Gibson, L. J., and M. F. Ashby. *Cellular Solids: Structure and Properties*. 2nd ed. Cambridge University Press, © 1997. Figure courtesy of Lorna Gibson and Cambridge University Press.

## Relative Density

$\rho^*$  = density of cellular solid

$\rho_s$  = density of solid it made from

$$\frac{\rho^*}{\rho_s} = \frac{M_s}{V_T} \frac{V_s}{M_s} = \frac{V_s}{V_T} = \text{volume fraction of solid (= 1-porosity)}$$


### Typical values:

collagen - GAG scaffolds:  $\rho^*/\rho_s = 0.005$


typical polymer foams:  $0.02 < \rho^*/\rho_s < 0.2$

soft woods:  $0.15 < \rho^*/\rho_s < 0.4$

- As  $\rho^*/\rho_s$  increases, cell edges (and faces) thicken, pore volume decreases
- In limit isolated pores in solid

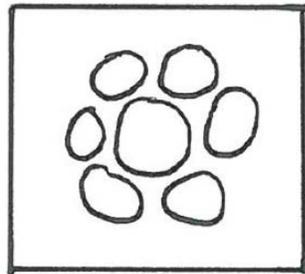

$\rho^*/\rho_s < 0.3$   
cellular solid

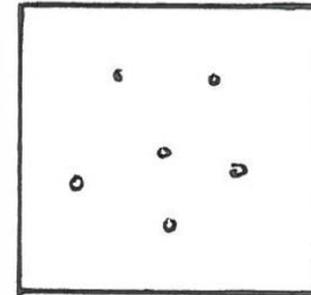

$\rho^*/\rho_s > 0.8$   
isolated pores in solid

# Unit Cells

2D honeycombs:      - Triangles, squares, hexagons      Fig.2.11  
                         - Can be stacked in more than one way  
                         - Different number of edges/vertex  
                         - Fig. 2.11 (a)-(e) isotropic; others anisotropic

3D foams:              Rhombic dodecahedra and tetrakaidecahedra pack to fill space      Fig.2.13  
                         (apart from triangles, squares, hexagons and prisms)

[Greek: hedron = face; do = 2; deca = 10; tetra = 4; kai = and]


Tetrakaidecahedra - bcc packing; geometries in Table 2.1

- Foams often made by blowing gas into a liquid
- If surface tension is only controlling factor and if it is isotropic, then the structure is one that minimizes surface area at constant volume


**Kelvin (1887):** tetrakaidecahedron with slightly curved faces is the single unit cell that packs to fill space plus minimizes surface area/volume      Fig.2.4

**Weaire-Phelan (1994):** identified cell made up of 8 polyhedra that has slightly lower surface area/volume (obtained using numerical technique - surface evolver )


# Unit Cells: Honeycombs

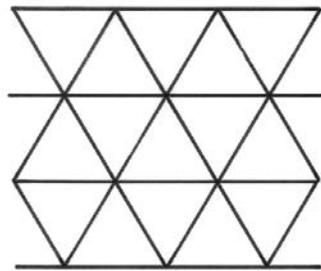


(a)

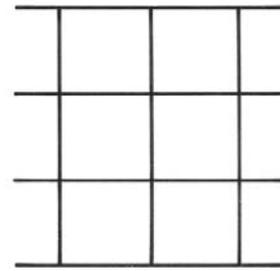


(c)

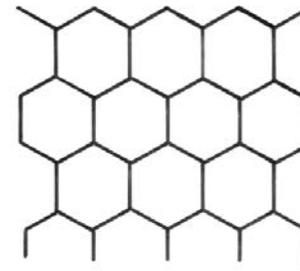


(e)

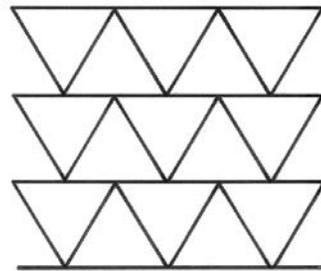

(b)

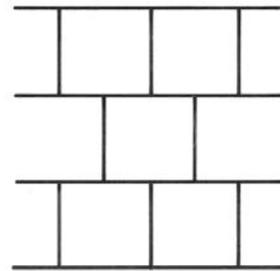


(d)

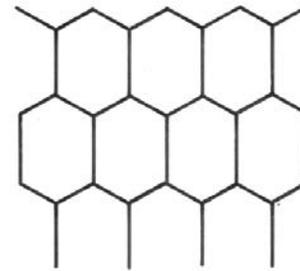

(f)


Gibson, L. J., and M. F. Ashby. *Cellular Solids: Structure and Properties*. 2nd ed. Cambridge University Press, © 1997. Figure courtesy of Lorna Gibson and Cambridge University Press.

# Unit Cells: Foams

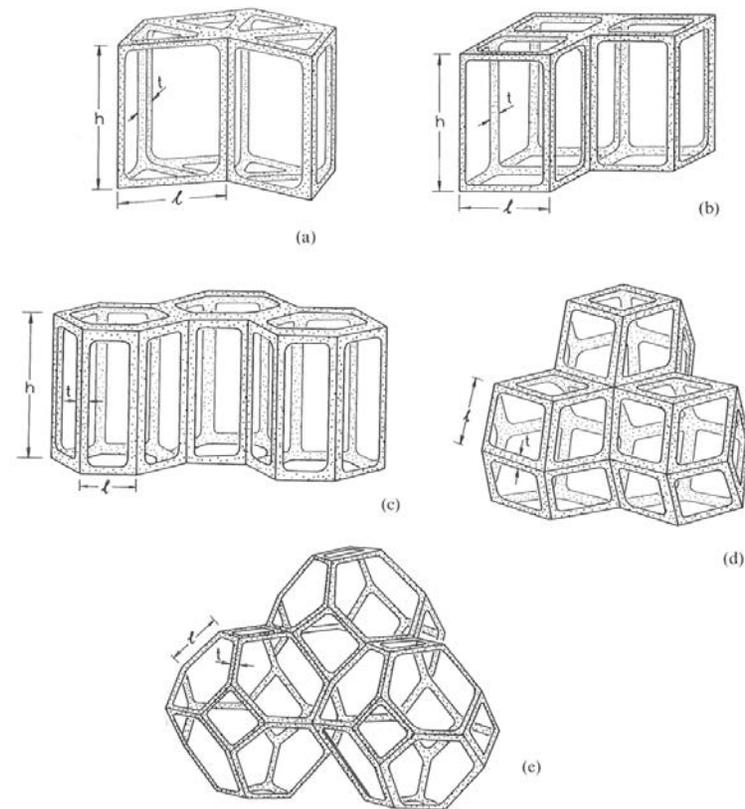

Gibson, L. J., and M. F. Ashby. *Cellular Solids: Structure and Properties*. 2nd ed. Cambridge University Press, © 1997. Figure courtesy of Lorna Gibson and Cambridge University Press.


# Unit Cells: Kelvin Tetrakaidcahedron

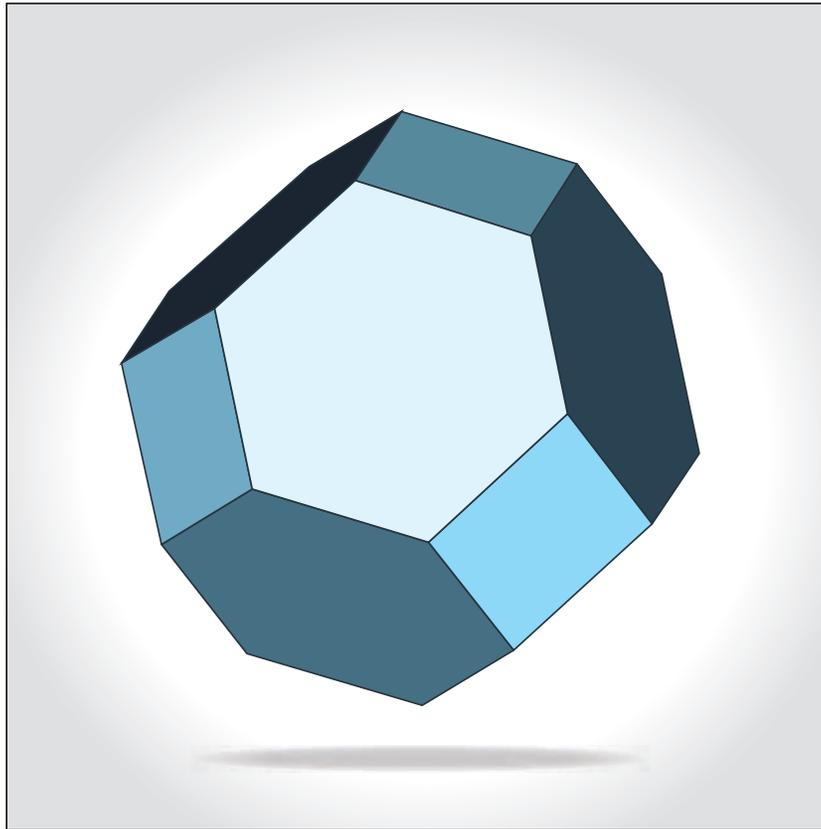

Kelvin's tetrakaidcahedral cell.

Source: Professor Denis Weaire; Figure 2.4 in Gibson, L. J., and M. F. Ashby.  
*Cellular Solids Structure and Properties*. Cambridge University Press, 1997.

# Unit Cells: Weaire-Phelan

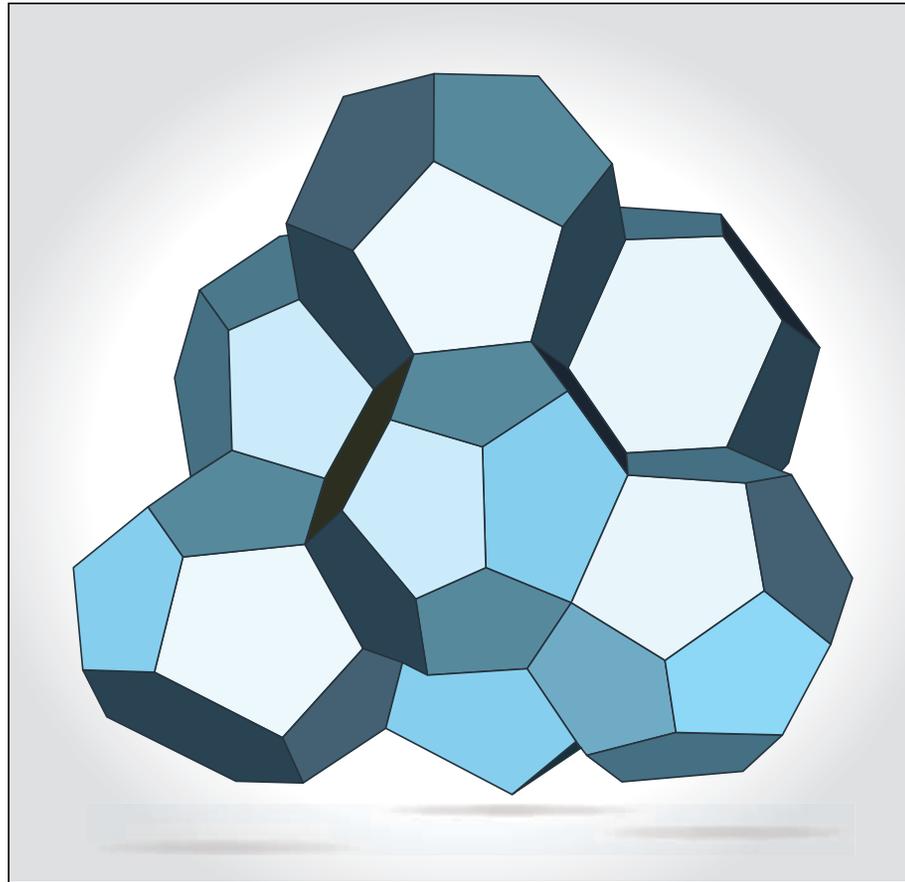

Weaire and Phelan's unit cell.

Source: Professor Denis Weaire; Figure 2.4 in Gibson, L. J., and M. F. Ashby.  
*Cellular Solids: Structure and Properties*. Cambridge University Press, 1997.


# Voronoi Honeycombs and Foams

- Foams sometimes made by supersaturating liquid with a gas and then reducing the pressure, so that bubbles nucleate and grow
- Initially form spheres; as they grow, they intersect and form polyhedral cells
- Consider an idealized case: bubbles all nucleate randomly in space at the same time and grow at the same linear rate
  - obtain Voronoi foam (2D Voronoi honeycomb)
  - Voronoi structures represent structures that result from nucleation and growth of bubbles
- Voronoi honeycomb is constructed by forming perpendicular bisectors between random nucleation points and forming the envelope of surfaces that surround each point
- Each cell contains all points that are closer to its nucleation point than any other
- Cells appear angular
- If specify exclusion distance (nucleation points no closer than exclusion distance) then cells less angular and of more similar size

Fig.2.14a


Fig.2.14b

# Voronoi Honeycomb

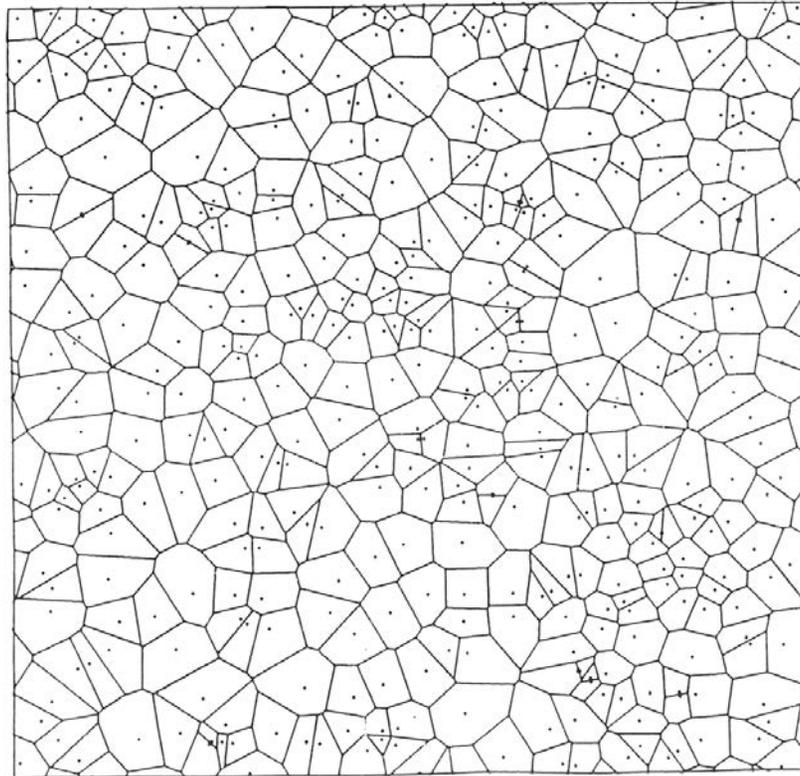

Gibson, L. J., and M. F. Ashby. *Cellular Solids: Structure and Properties*. 2nd ed. Cambridge University Press, © 1997. Figure courtesy of Lorna Gibson and Cambridge University Press.


# Voronoi Honeycomb with Exclusion Distance

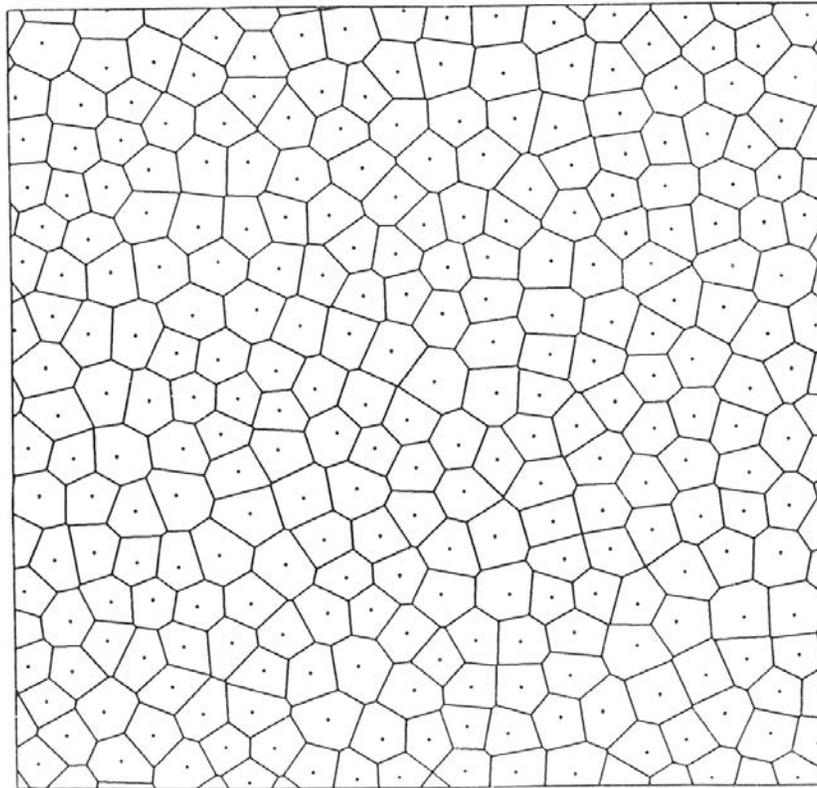


Gibson, L. J., and M. F. Ashby. *Cellular Solids: Structure and Properties*. 2nd ed. Cambridge University Press, © 1997. Figure courtesy of Lorna Gibson and Cambridge University Press.

# Cell Shape, Mean Intercept Length, Anisotropy

## Honeycombs

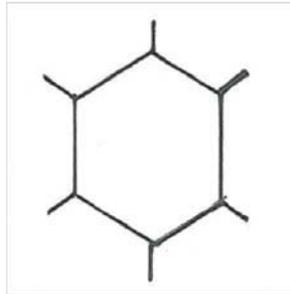

regular hexagon:  
isotropic in plane

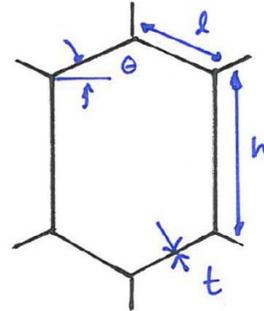

elongated hexagon: anisotropic  
 $h/l, \theta$  define cell shape

## Foams

- Characterize cell shape, orientation by mean intercept lengths
- Consider circular test area of plane section
- Draw equidistant parallel lines at  $\theta = 0^\circ$
- Count number of intercepts of cell wall with lines:

$N_c$  = number of cells per unit length of line

$$L(\theta = 0^\circ) = \frac{1.5}{N_c}$$

Huber  
paper  
Fig.9

# Mean Intercept Length

Figures removed due to copyright restrictions.

See Fig. 9: Huber, A. T., and L. J. Gibson. "[Anisotropy of Foams](#)." *Journal of Materials Science* 23 (1988): 3031-40.

## Mean intercept

- Increment  $\theta$  by some amount (eq.  $5^\circ$ ) and repeat
- Plot polar diagram of mean intercept lengths as  $f(\theta)$
- Fit ellipse to points (in  $3D$ , ellipsoid)
- Principal axes of ellipsoid are principal dimensions of cell
- Orientation of ellipse corresponds to orientation of cell
- Equation of ellipsoid:  $Ax_1^2 + Bx_2^2 + Cx_3^2 + 2Dx_1x_2 + 2Ex_1x_3 + 2Fx_2x_3 = 1$
- Write as matrix M: 
$$M = \begin{bmatrix} A & B & E \\ D & B & F \\ E & F & C \end{bmatrix}$$
- Can also represent as tensor “fabric tensor”
- If all non-diagonal elements of the matrix are zero, then diagonal elements correspond to principal cell dimensions

## Connectivity

- *Vertices* connected by *edges* which surround *faces* which enclose *cells*
- Edge connectivity,  $Z_e =$  number of edges meeting at a vertex  
typically  $Z_e = 3$  for honeycombs  
 $Z_e = 4$  for foams
- Face connectivity,  $Z_f =$  number of faces meeting at an edge  
typically,  $Z_f = 3$  for foams

## Euler's Law

- Total number of vertices,  $V$ , edges,  $E$ , faces,  $F$ , and cells,  $C$  is related by Euler's Law (for a large aggregate of cells):

$$2D : F - E + V = 1$$

$$3D : -C + F - E + V = 1$$

For an irregular, 3-connected honeycomb (with cells with different number of edges), what is the average number of sides/face,  $\bar{n}$ ?

$$Z_e = 3 \quad \therefore E/V = 3/2 \text{ (each edge shared between 2 vertices)}$$

If  $F_n$  = number of faces with  $n$  sides, then:

$$\sum \frac{nF_n}{2} = E \text{ (factor of 2 since each edge separated two faces)}$$



**Using Euler's Law:**

$$F - E + \frac{2}{3}E = 1$$

$$F - \frac{1}{3} \sum \frac{nF_n}{2} = 1$$

$$6F - \sum nF_n = 6$$

$$6 - \frac{\sum nF_n}{F} = \frac{6}{F}$$

As  $F$  becomes large, RHS  $\rightarrow 0$


$$\frac{\sum nF_n}{F} = \text{average number of sides per face, } \bar{n}$$

$$\bar{n} = 6$$

For 3-connected honeycomb, average number of sides *always* 6.

Fig.2.9a

# Euler's Law

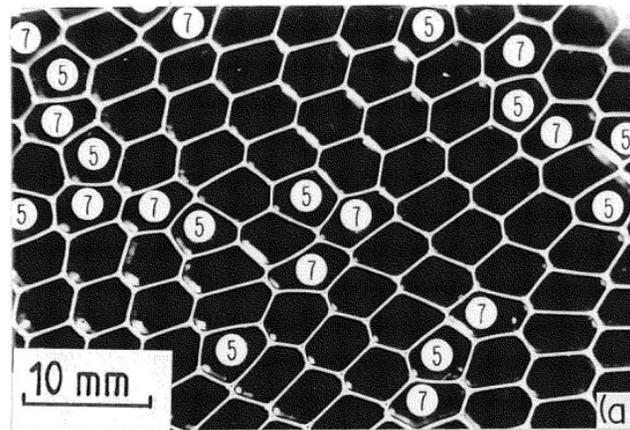

Gibson, L. J., and M. F. Ashby. *Cellular Solids: Structure and Properties*. 2nd ed. Cambridge University Press. © 1997. Figure courtesy of Lorna Gibson and Cambridge University Press.

## Soap Honeycomb

## Aboav-Weaire Law

- Euler's Law: for 3-connected honeycomb, average number of sides/face=6
- Introduction of a 5-sided cell requires introduction of 7-sided cell, etc
- Generally, cells with more sides (in  $2D$ ) (or faces, in  $3D$ ) than average, have neighbors with fewer sides (in  $2D$ ) (or faces, in  $3D$ ) than average
- **Aboav** - observation in  $2D$  soap froth  
**Weaire** - derivation
- $2D$ : If a candidate cell has  $n$  sides, then the average number of sides of its  $n$  neighbors is  $\bar{m}$ :

$$\bar{m} = 5 + \frac{6}{n} \quad (2D)$$

## Lewis' Rule

- Lewis examined biological cells and 2D cell patterns
- Found that area of a cell varied linearly with the number of its sides

$$\frac{A(n)}{A(\bar{n})} = \frac{n - n_0}{\bar{n} - n_0}$$

$A(n)$  = area of cell with  $n$  sides

$A(\bar{n})$  = area of cell with average number of sides,  $\bar{n}$

$n_0$  = constant (Lewis found  $n_0 = 2$ )

- Holds for Voronoi honeycomb; Lewis found holds for most of other 2D cells
- Also, in 3D:

$$\frac{V(f)}{V(\bar{f})} = \frac{f - f_0}{\bar{f} - f_0}$$

$V(f)$  = volume of cell with  $f$  faces

$V(\bar{f})$  = volume of cell with average number of faces,  $\bar{f}$

$f_0$  = constant,  $\approx 3$

## Modeling cellular solids - structural analysis

Three main approaches:

1. Unit cell

- E.g. honeycomb-hexagonal cells
- Foam - tetrakaidecahedra (but cells not all tetrakaidecahedra)

2. Dimensional analysis

Foams - complex geometry, difficult to model exactly

- instead, model mechanisms of deformation and failure (do not attempt to model exact cell geometry)

3. Finite element analysis

- Can apply to random structures (e.g., 3D Voronoi) or to micro-computed tomography information.
- Most useful to look at local effects (e.g., defects - missing struts - osteoporosis size effects)

MIT OpenCourseWare  
<http://ocw.mit.edu>

3.054 / 3.36 Cellular Solids: Structure, Properties and Applications  
Spring 2015

For information about citing these materials or our Terms of Use, visit: <http://ocw.mit.edu/terms>.